

Online Research @ Cardiff

This is an Open Access document downloaded from ORCA, Cardiff University's institutional repository: <https://orca.cardiff.ac.uk/id/eprint/129518/>

This is the author's version of a work that was submitted to / accepted for publication.

Citation for final published version:

Hong, John, Lee, Young-Woo, Hou, Bo ORCID: <https://orcid.org/0000-0001-9918-8223>, Ko, Wonbae, Lee, Juwon, Pak, Sangyeon, Hong, JinPyo, Morris, Stephen M., Cha, SeungNam, Sohn, Jung Inn and Kim, Jong Min 2016. Solubility-dependent NiMoO₄ nanoarchitectures: direct correlation between rationally designed structure and electrochemical pseudokinetics. ACS Applied Materials and Interfaces 8 (51) , pp. 35227-35234. 10.1021/acsami.6b11584 file

Publishers page: <http://dx.doi.org/10.1021/acsami.6b11584>
<<http://dx.doi.org/10.1021/acsami.6b11584>>

Please note:

Changes made as a result of publishing processes such as copy-editing, formatting and page numbers may not be reflected in this version. For the definitive version of this publication, please refer to the published source. You are advised to consult the publisher's version if you wish to cite this paper.

This version is being made available in accordance with publisher policies.

See

<http://orca.cf.ac.uk/policies.html> for usage policies. Copyright and moral rights for publications made available in ORCA are retained by the copyright holders.



**Solubility-dependent NiMoO₄ nanoarchitectures: Direct correlation between rationally
designed structure and electrochemical pseudo-kinetics**

John Hong^a, Young-Woo Lee^a, Bo Hou^a, Wonbae Ko^b, Juwon Lee^a, Sangyeon Pak^a,

JinPyo Hong^b, Stephen M. Morris^a, SeungNam Cha^{a,*}, Jung Inn Sohn^{a,*} and Jong Min Kim^c

^a Department of Engineering Science, University of Oxford, Parks Road, Oxford, OX1 3PJ, United Kingdom.

^b Research Institute of Convergence of Basic Science, Novel Functional Materials and Device Laboratory, Department of Physics, Hanyang University, Seoul 133-791, Korea.

^c Electrical Engineering Division, Department of Engineering, University of Cambridge, 9 JJ Thomson Avenue, Cambridge, CB3 0FA, United Kingdom.

* Corresponding author. Tel: +44-1865-273912. Fax: +44-1865-273010.

E-mail address: seungnam.cha@eng.ox.ac.uk; junginn.sohn@eng.ox.ac.uk.

Abstract

Pseudocapacitors have recently attracted attention from the scientific community as a promising new energy storage system, which can potentially bridge the performance gap between lithium ion batteries and conventional capacitors. To further improve the performance of these pseudocapacitors, tailoring the binary metal oxide along with developing new methods for controlling resultant nanostructures in a predictive way is an essential requirement for achieving more favorable electrochemical kinetics. Here, through a simple hydrothermal synthetic procedure that uses different supersaturation states to alter the driving force for crystal growth, we have managed to obtain one-dimensional (1-D) Nickel Molybdenum Oxide (NiMoO_4) electrodes on a nickel foam. The morphology of the 1-D NiMoO_4 nanostructures can be tuned from a low to a high aspect ratio (over a range of diameter sizes from 80 to 800 nm). Such a controllable structure provides a platform for understanding the electrochemical relationships in terms of fast retention times and improved ion diffusion coefficients, enabling the demonstration of promising electrochemical storage properties. We show that the 1-D NiMoO_4 electrode with a high aspect ratio (HAR) exhibits a much higher specific capacitance of 1335 F g^{-1} at a current density of 1 A g^{-1} , which is due to the unique physical and chemical structure being suitable for electrochemical kinetics. We further demonstrate that an asymmetric supercapacitor consisting of the tailored HAR- NiMoO_4 electrode can achieve an energy density of 40.7 Wh kg^{-1} and a power density of 16 kW kg^{-1} .

Keywords: Energy storage material, Electrochemical reaction kinetics, Nanowire architecture, Controlled aspect ratio, Asymmetric supercapacitor

1. INTRODUCTION

Electrochemical supercapacitors are currently being considered as promising candidates for next-generation energy storage applications since they have the potential to bridge the gap between batteries and conventional capacitors for the production of high power and high energy densities. Furthermore, they have been shown to exhibit a good rate capability, long cycling life time, and environmentally friendly characteristics.¹⁻³ In particular, pseudocapacitors, which possess the capability to store large amounts of charge *via* fast and reversible electrochemical Faradaic redox reactions, have enormous potential in a broad variety of applications, including electric vehicles and portable electronic devices.^{4,5} Currently, transition metal oxides/hydroxides such as RuO_2 , Ni(OH)_2 , Co_3O_4 and MnO_2 , are most commonly used as the electrode materials with high theoretical capacitances because of their multiple oxidation states, enabling rich electrochemical Faradaic reactions.⁶⁻⁹

Despite their compelling benefits combined with the inherently high electrochemical activities, their low conductivity and structural instability, which leads to a reduction in the performance, continuously hinders the successful exploitation of pseudocapacitor technology in practical applications.¹⁰ To overcome these limitations, numerous studies have been devoted to enhancing the electrochemical properties of the pseudocapacitors by focusing on the development of new electrode materials that are based on binary transition metal oxides.¹¹⁻¹⁴ These materials typically exhibit a higher electrical conductivity and richer chemical valence states than the single-component transition metal oxides, which arises from the combined contributions from both metal atoms.¹¹⁻¹⁴ Among the various binary metal oxides, transition metal molybdates such as NiMoO_4 and CoMoO_4 are an emerging class of pseudocapacitor materials that have received considerable attention due to their cost-effectiveness, abundance, and chemical stability.^{15,16} More specifically, the primary interest in NiMoO_4 lies in the fact that the high specific capacitance from the Ni atom and the high

1
2
3
4 electrical conductivity from the Mo atom can contribute collectively to the superior
5
6 electrochemical behavior when used in energy storage devices.¹⁷ Combined, these features
7
8 demonstrate that NiMoO₄ has potential in future pseudocapacitor energy storage systems.
9

10
11 Alternatively, various nanostructuring approaches have been developed to address
12
13 issues related to limited electrochemical kinetics on the surface, which are strongly associated
14
15 with a low degree of surface contact areas and low ion diffusion rates.¹⁸⁻¹⁹ These more recent
16
17 strategies have shown that hierarchical nanostructures with diverse morphologies and
18
19 dimensions (D) can provide more active sites and shorter ion diffusion pathways, which then
20
21 stimulate and facilitate the kinetics associated with the electrochemical reactions. In
22
23 particular, 1-D nanostructures are one of the most widely used architectures for
24
25 electrochemical storage devices mainly because 1) the unique geometry results in a large
26
27 contact surface area; 2) the structures exhibit short diffusion distance; 3) they exhibit good
28
29 structural stability and 4) they possess a favorable charge carrier path during the
30
31 charge/discharge processes. Nevertheless, synthesizing these 1-D structures in binary metal
32
33 oxides in a controlled way still remains a challenge and is mainly due to the complex
34
35 stoichiometry-dependent synthetic reactions. Further, even though there have been few
36
37 reports²⁰⁻²¹ that have studied the dependence of the electrochemical storage performance on
38
39 the different nanostructures, there are no detailed studies that directly describe the
40
41 electrochemical ion intercalation mechanism for engineering 1-D nanostructures with tailored
42
43 aspect ratios.
44
45
46
47
48

49
50 It is, therefore, highly desirable that a novel and facile synthetic route for the
51
52 preparation of 1-D nanostructured binary metal oxides with different aspect ratios be
53
54 developed that can enhance the charge transfer kinetics so as to improve charge
55
56 transportation. Moreover, developing such a procedure would enable us to understand how
57
58 the charge storage dynamics and electrochemical stability depends upon the nanostructure
59
60

and how this can lead to a superior pseudocapacitor performance. To this end, we have employed the fundamental principle of hydrothermal reaction kinetics whereby the nucleation and crystallization growth rates can depend crucially on the supersaturation states of the solvents, which are the major driving forces for solution-based synthetic processes as shown in Figures 1a-c.²² Controlling the rational supersaturated environments enables the synthesis of 1-D NiMoO₄ nanostructures with different, but predictable, morphologies. In this regard, we propose a simple and facile way for the rational and precise design of the desirable supersaturation levels, which in turn affects the crystal nucleation rates and preferred crystal growth geometries and directions thereby leading to different 1-D aspect ratios. Moreover, the different 1-D NiMoO₄ nanostructures can result in a diverse range of electrochemical behavior including specific capacitance as well as ion diffusion and charge transfer dynamics. Through the control of these properties, it therefore provides one of the best routes for the design of new electrode materials for high-performance supercapacitors.

2. EXPERIMENTAL DETAILS

2.1 Material synthesis: NiMoO₄ nanostructures on a Ni foam.

Different 1-D NiMoO₄ nanostructures with different aspect ratios on nickel foams were synthesized by a hydrothermal method. First, a conductive Ni foam (1 cm x 1 cm) was cleaned using 1 M HCl, ethanol, and deionized water. In a typical synthesis, 1.0 mmol of Ni(NO₃)₂·6H₂O and 1.0 mmol of Na₂MoO₄ were dissolved in deionized water at room temperature to form a clear green solution. After being stirred for an hour, the solution was transferred into a 45 ml Teflon-lined cup, and then the Ni foam was transferred into the Teflon-lined cup and a stainless steel autoclave. The hydrothermal reaction was carried out at 140 °C for 4 hr. After cooling down naturally to room temperature, the Ni foam was collected and washed several times with water and ethanol to remove loosely attached NiMoO₄ on the

1
2
3
4 Ni foam. The foam was then fully dried at 60 °C for 12 hr. In order to obtain the crystallized
5
6 NiMoO₄ nanostructures, the Ni foam with the NiMoO₄ nanostructure was calcined at 400 °C
7
8 for 2 hr in an argon atmosphere. The different nanostructures of the NiMoO₄ material were
9
10 synthesized using various solvents with different mixtures of solvents such as water, ethanol
11
12 and hydrochloric acids.
13

14 15 **2.2 Material characterization**

16
17 Morphologies of the samples were characterized by SEM (Hitachi S-4300) and TEM
18
19 (JEOL JEM-2200MCO FEGTEM). The crystal structure of the samples was examined by
20
21 high resolution XRD (Rigaku Medel Smartlab) in a two theta range of 10-80°. The specific
22
23 BET surface area was calculated on the basis of nitrogen adsorption isotherms using
24
25 Micromeritics Gemini VI. XPS were recorded using a Thermo Scientific K-Alpha XPS
26
27 instrument equipped with a micro-focused mono-chromated Al X-ray source. The XPS
28
29 source was operated at 12 keV and a 400 μm spot size was used. The spectrometer was
30
31 adjusted to align a binding energy of 284.5eV for the C 1s line.
32
33
34

35 **2.3 Electrochemical characterization**

36
37 The electrochemical properties of the NiMoO₄ samples with different aspect ratios
38
39 were measured in a three-electrode system consisting of HAR-, MAR-, and LAR-NiMoO₄
40
41 electrodes as working electrodes, Pt mesh as a counter electrode, and an Ag/AgCl electrode
42
43 (in saturated 3 M KCl) as a reference electrode. These were used to analyze CV, galvanostatic
44
45 charge/discharge, and EIS curves using a potentiostat (PGSTAT302N, Metrohm, Autolab).
46
47 For the fabrication of the anode electrodes, active carbon was prepared as an active material,
48
49
50 with poly(vinylidene difluoride) as a binder and Ketjen black as a conductive material, and
51
52 this was then coated onto the compressed nickel foam as a current collector. All
53
54 electrochemical results of the AC//HAR-NiMoO₄ ASC were measured using a two electrode
55
56 system under 1.0 M KOH solution at room temperature.
57
58
59
60

3. RESULTS AND DISCUSSION

The morphology and structural characteristics of the as-prepared NiMoO_4 materials were investigated by scanning electron microscopy (SEM). As shown in Figures 1d-f, the controlled growth of the 1-D NiMoO_4 nanostructures with different aspect ratios was successfully achieved on a nickel foam through a hydrothermal process by adjusting the solubility level in the reaction solution and hence introducing various different supersaturation states during the growth phase. Obviously, as the relative solubility decreases, the morphology of the 1-D nanostructures is transformed through a series of distinct aspect ratios between length to breadth from a low (LAR) to a high value (HAR) through a medium value (MAR). Figure 1d shows an SEM image of the MAR- NiMoO_4 sample obtained from the DI water-only solution, which results in 1-D nanostructures with a diameter size of ~250 nm. In contrast, the HAR- NiMoO_4 sample with a diameter of about 80 nm is grown under low solubility conditions induced by adding an alkaline solvent into the water solution (Figure 1e). Finally, the LAR- NiMoO_4 sample has a diameter of 800 nm and was constructed by introducing an additional acidic solvent (Figure 1f). These findings indicate that introducing a low (high) solubility environment to the hydrothermal precursor solution induces the relatively high (low) degree of supersaturation, leading to a higher (lower) driving force for crystal nucleation and growth process. Therefore, the selective synthesis mechanism responsible for the different 1-D NiMoO_4 structures can be understood in terms of the control of the solvent solubility that leads to different degrees of supersaturation. Moreover, a predictable 1-D nanostructure synthetic route so as to grow the active materials directly on to a metal collector means that the driving force for nucleation and crystal growth can be controlled by changing the supersaturation states.

Next, the nanostructures of the HAR-, MAR- and LAR- NiMoO_4 samples were

1
2
3
4 further characterized by transmission electron microscopy (TEM) to provide more insight
5
6 regarding their unique 1-D structure, as shown in inset images of Figures 1d-f. The TEM
7
8 images clearly demonstrate that the diameter of 1-D nanostructures for the as-prepared
9
10 NiMoO₄ samples is in good agreement with the SEM results. As a result of tuning the
11
12 solubility of the solvents, three different types of 1-D NiMoO₄ material with mean aspect
13
14 ratios of 21.6 (HAR-NiMoO₄), 12.8 (MAR-NiMoO₄), and 4.7 (LAR-NiMoO₄) were
15
16 successfully prepared for use in a supercapacitor application (Supporting Information Figure
17
18 S1).
19

20
21
22 To evaluate the crystallographic phase of the NiMoO₄ electrode samples, X-ray
23
24 diffraction (XRD) spectra were analyzed, which are shown in Figure 2a. All the diffraction
25
26 patterns obtained from the 1-D NiMoO₄ nanostructures with different aspect ratios are
27
28 unambiguously assigned to the NiMoO₄ phase (JCPDS Card No. 86-0361) without any
29
30 noticeable differences.²³ Moreover, to confirm the surface electronic states and chemical
31
32 compositions of the NiMoO₄ samples, X-ray photoelectron spectroscopy (XPS)
33
34 measurements were carried out. Figures 2c-d compare the high resolution XPS spectra of the
35
36 Ni 2p and Mo 3d of the 1-D NiMoO₄ samples with different aspect ratios, respectively. The
37
38 Ni 2p doublet is clearly observed at 854.9 eV (Ni²⁺ 2p_{3/2}) and at 872.5 eV (Ni²⁺ 2p_{1/2}) with a p
39
40 spin-orbit splitting of 17.6 eV.²⁴ Moreover, the two peaks at binding energies of 232.0 eV and
41
42 235.1 eV with the d spin-orbit splitting of 3.1 eV correspond to Mo⁶⁺ 3d_{5/2} and Mo⁶⁺ 3d_{3/2},
43
44 respectively.²⁵ These XPS results suggest that there are only chemical oxidation states and
45
46 compositions of the Ni²⁺ and Mo⁶⁺ in the as-prepared 1-D NiMoO₄ whereby the Ni cations,
47
48 distributed in octahedral sites, are electrochemically active with OH⁻ electrolyte ions and the
49
50 Mo cations in tetrahedral sites contribute to the electrochemical stability.
51
52
53
54

55 To further examine the specific surface area characteristics of the 1-D NiMoO₄
56
57 structures, measurements of the N₂ adsorption-desorption were carried out (Supporting
58
59
60

Information Figure S2). As shown in Figure 2b, the calculated Brunauer-Emmett-Teller (BET) surface area of the HAR-NiMoO₄ sample has the largest value (97.26 m² g⁻¹) and is much larger than the areas for the MAR-NiMoO₄ (50.32 m² g⁻¹) and LAR-NiMoO₄ (25.66 m² g⁻¹) samples, which is mainly due to the different aspect ratios of the nanostructures. This implies that the high surface area of the HAR-NiMoO₄ electrodes provides a sufficient electrolyte contact interface and can thus enhance the kinetics of ion diffusion. Consequently, a high aspect ratio can improve the electrochemical capacitance and the charge transfer kinetics.

In order to evaluate the electrochemical performance of the different 1-D morphologies, the HAR-, MAR- and LAR-NiMoO₄ were applied directly as working electrodes in a three electrode system. Supporting Information Figure S3 shows the cyclic voltammetry (CV) and the galvanostatic charge-discharge curves of the each NiMoO₄ electrode. First, the CV curves of all the NiMoO₄ electrodes have similar shapes with increasing scan rates, indicating that all the electrodes have good pseudocapacitive behavior.²⁶ For a direct CV performance comparison between the electrodes, Figure 3a presents the CV curves of the three different types of NiMoO₄ electrodes with the potential window ranging from 0.0 to 0.6 V at a scan rate of 5 mV s⁻¹. It can be clearly observed that all the NiMoO₄ electrodes have a couple of Faradaic reaction peaks that can be ascribed to the reversible redox reaction between Ni(II) and Ni(III).²⁷ The area surrounded within the CV curve of the HAR-NiMoO₄ sample occupies the largest area, indicating the highest value for the electrochemical capacitance. This large CV area might be attributed to the larger electrolyte contact area for the HAR-NiMoO₄ electrode. Consistent with the CV results, the galvanostatic charge-discharge curves demonstrate that the HAR-NiMoO₄ electrode has the longest discharge time (Supporting Information Figure S3). Moreover, the calculated specific capacitance of the HAR-, MAR-, and LAR-NiMoO₄ samples at a current density of 1 A g⁻¹

are 1335 F g⁻¹, 1106 F g⁻¹ and 672 F g⁻¹, respectively (Supporting Information Figure S4).

In order to better understand the ion diffusion behavior and charge transfer dynamics of the NiMoO₄ electrodes with tailored aspect ratios, kinetic electrochemical analysis was carried out. The inset of Figure 3a indicates the potential difference of each electrode between the anodic and cathodic peak, representing the degree of reversible intercalation and de-intercalation dynamics during the CV charge-discharge.²⁸ It can be seen that the HAR-NiMoO₄ electrode provides a much more appreciable OH⁻ ion access and faster charge transfer rate. Moreover, the cathodic peak current densities of the NiMoO₄ electrodes were plotted as a function of the square root of the scan rates in Figure 3b. The cathodic peak currents increase linearly, showing that redox reactions at the surface are followed by a diffusion-controlled process with the OH⁻ ions.²⁹ Also, it is evident that the cathodic peak current of the HAR-NiMoO₄ sample shows a steeper dependence compared to the other electrodes, indicating a larger diffusion coefficient. For a direct comparison of the ion diffusivity, the diffusion coefficients of the NiMoO₄ electrodes were calculated according to the following Randles-Sevcik equation.³⁰

$$i_p = (2.69 * 10^5) * n^{\frac{3}{2}} * A * D_0^{\frac{1}{2}} * C_0 * v^{\frac{1}{2}}$$

where i_p is the cathodic peak current density, n is the number of electrons, A is the electrode area, D_0 is the diffusion coefficient, C_0 is the electrolyte concentration, and v is the scan rate. We can assume that n , A , C_0 have the same values in the same three electrode system. Therefore, the diffusion coefficient of the 1-D NiMoO₄ samples can be directly compared from the slope of the curve ($D_0^{\frac{1}{2}} \propto i_p/v^{\frac{1}{2}}$). The diffusion coefficient of the HAR-NiMoO₄ sample is found to be 1.82 and 17.9 times larger than that of the MAR- and LAR-NiMoO₄ samples, respectively.

Figure 3c presents the specific rate retention data as a function of the current density

in the electrodes. From a low current density of 1 A g^{-1} to a high current density of 20 A g^{-1} , the capacitance of the HAR-NiMoO₄ electrode shows good rate retention behavior, which is found to be 882.4 F g^{-1} at 20 A g^{-1} with $\sim 66.1 \%$ retention compared to that for 1 A g^{-1} . On the other hand, for the MAR and LAR-NiMoO₄ electrodes the capacitance is recorded to be 668.8 F g^{-1} and 146.0 F g^{-1} with 60.5% and 21.8% rate retention, respectively. In other words, the presence of the fast diffusion rate from the surface to the internal structure means that the HAR-NiMoO₄ electrode exhibits much better retention performance.

Finally, to elucidate further the ion diffusion and charge transfer behavior, electrochemical impedance spectroscopy (EIS) measurements with Bode phase plots and Nyquist plots were conducted and plotted, respectively (Figure 3d and Supporting Information Figures S5). All the Nyquist plots for the NiMoO₄ electrodes show that the charge transfer resistances (R_{ct}), recorded from the diameters of the semicircle, are very low. This outcome demonstrates that the NiMoO₄ electrodes grown directly on the Ni foam current collector have nearly equal electrolyte resistance and superior charge transfer, which minimizes interfacial resistance and facilitates charge transfer at the interface between the current collector and electrode material. Furthermore, the linear part in the plot of the HAR-NiMoO₄ sample in the low frequency region (Warburg impedance) is significantly steeper than that for the MAR- and LAR-NiMoO₄ samples, suggesting that the HAR-NiMoO₄ has the fastest ion diffusion and electrolyte access to the surface, which is consistent with the results of the capacitance rate retention in Figure 3c.³¹

Figure 3d shows the Bode phase plots for the NiMoO₄ electrodes with the different relaxation time constant (τ_0). A relaxation time constant can be calculated from the x-axis frequency when the curve reaches -45° on the Bode plot. The relaxation time constant is an important parameter so as to compare between capacitive and resistive behaviors of a supercapacitors dependence on frequency.³² As shown in Figure 3d, the HAR-NiMoO₄

sample exhibits the fastest relaxation time constant ($\tau_0 = 1.73$ s) compared to that of the MAR- and LAR-NiMoO₄ samples which are 3.49 s and 6.87 s, respectively. Here, it should be noted that the fast relaxation time constant implies that the HAR-NiMoO₄ sample can introduce a fast capacitive response. It can be clearly observed that the phase angle of HAR-NiMoO₄ at a low frequency of $f = 0.01$ Hz was about -81° , which is the closest value to -90° , implying ideal capacitor behavior because of its low electrolyte resistance and fast electrolyte intercalation.³³ Overall, the electrochemical relationships for the NiMoO₄ electrodes with the different 1-D morphologies are illustrated in Figure 3e. The HAR-NiMoO₄ electrode nanostructure not only provides the largest contact sites, which lead to a large density of electrolyte ions near the surface, but also facilitates more efficient electrochemical reactions through the highest degree of ion diffusion towards the inside of the electrode. Additionally, its high electrical conductivity and low surface resistance enable fast charge transfer through a pseudocapacitor system. Such behavior is strongly correlated to the high capacitance, fast retention rate and charge transfer mechanism of the HAR-NiMoO₄ electrode.

To further demonstrate the potential of the NiMoO₄ electrode for practical supercapacitor applications, an asymmetric supercapacitor (ASC) was fabricated using the HAR-NiMoO₄ material as the cathode and active carbon (AC) as the anode. Figure 4a shows the comparative CV plots of the individual positive and negative electrodes in the ASC at a scan rate of 5 mV s^{-1} . The AC exhibits a typical rectangular electric double-layer capacitor (EDLC) performance within the range of -1.0 to 0.0 V, and the HAR-NiMoO₄ shows pseudocapacitance behavior within the range of 0.0 to 0.6 V. Therefore, the AC//HAR-NiMoO₄ ASC can operate from 0 to 1.6 V with a wide operating potential. To design the ASC with the ideal capacitance, the mass of the individual electrodes is optimized according to the following formula.³⁴

$$Q_+ = Q_- \rightarrow \frac{m_+}{m_-} = \frac{C_- * \Delta V_-}{C_+ * \Delta V_+}$$

where C_- and C_+ are the calculated capacitance of the negative and positive electrodes, respectively, and ΔV_- and ΔV_+ are the operating potential windows of the negative and positive electrodes, respectively. Therefore, on the basis of C_- and the potential window of the AC electrode, the optimum loading ratio of HAR-NiMoO₄ to AC is 1:3.126.

Figure 4b shows CV curves of the ASC device at various scan rates, ranging from 50 to 5 mV s⁻¹. It can be seen that the shape of the CV curves involves both EDLC and pseudocapacitance contribution from the rectangular shape and the redox humps. The CV curves of the ASC are found to maintain a similar profile with increasing scan rates, indicating good capacitive behavior. As shown in the inset of Figure 4c, galvanostatic charge/discharge curves for the ASC were measured at current densities from 1 to 20 A g⁻¹ in a potential window of 0 to 1.6 V. In addition, the calculated capacitance as a function of the discharge current density is plotted (Supporting Information Figure S4). This device shows good electrochemical performance and the specific capacitance was calculated to be 114.4 F g⁻¹ at a current density of 1 A g⁻¹. Furthermore, the ASC exhibits good cycling stability, retaining up to 82.2 % after 2000 charge-discharge cycles at a current density of 5 A g⁻¹ (Figure 4c). To compare the energy density and power density with other reported ASCs, the Ragone plots of the AC//HAR-NiMoO₄ ASC were derived in Figure 4d, showing that an energy density of 40.6 Wh kg⁻¹ and a power density of 16 kW kg⁻¹ can be achieved. Clearly, the device performance compares favorably with other asymmetric supercapacitors.³⁵⁻⁴¹ It is shown that the HAR-NiMoO₄ exhibits a high specific capacitance and high ionic and electric transfer rates, along with good electrochemical behavior because: (1) the direct growth of the 1-D NiMoO₄ sample on the Ni foam provides good electron transfer due to the low contact resistance between the active material and the current collector; (2) the highly ordered 1-D

1
2
3
4 nanostructure with a high aspect ratio not only leads to a large diffusion coefficient, but also
5
6 results in a large contact area and (3) this gives rises to numerous ion diffusion channels,
7
8 thereby inducing a high rate retention response.
9

10 11 12 13 **CONCLUSION**

14
15 In summary, we have demonstrated that 1-D NiMoO₄ electrodes grown directly onto
16
17 a nickel foam have been successfully prepared via a simple supersaturation-controlled
18
19 hydrothermal process. The resulting 1-D NiMoO₄ electrodes, each with a different aspect
20
21 ratio, can be predictively adjusted by changing the supersaturation states and consequently
22
23 the driving force for nucleation and crystal growth. Moreover, electrochemical measurements
24
25 indicate that the HAR-NiMoO₄ electrode exhibits the best specific capacitance and superior
26
27 rate retention performance such as a large specific capacitance of 1335 F g⁻¹ at a current
28
29 density of 1 A g⁻¹ with a good rate retention of 66.1 %. We also showed that the AC//HAR-
30
31 NiMoO₄ ASC with a wide potential window of 1.6 V exhibits the energy density of 40.7 Wh
32
33 kg⁻¹ and the power density of 16 kW kg⁻¹ compared to other reported pseudo-capacitive
34
35 ASCs. Furthermore, we successfully demonstrated that the HAR-NiMoO₄ electrode provides
36
37 a better contact surface area, ion diffusion behavior and enhanced charge transfer kinetics
38
39 based on the hierarchical 1-D nanostructure. This deterministic and predictive synthesis
40
41 method, which is controlled by adjusting the solubility in a hydrothermal approach, is a
42
43 promising technique to producing highly efficient pseudo-capacitive electrodes with 1-D
44
45 nanostructures. Such electrodes can easily promote dynamic electrochemical kinetics,
46
47 including high Faradaic capacitance, high retention and fast charge transfer rate for practical
48
49 pseudocapacitor applications.
50
51
52
53
54
55
56
57
58
59
60

Acknowledgments

This work was supported by the Industrial Fundamental Technology Development Program from the Ministry of Trade, Industry and Energy (MOTIE) of Korea [10052745, Development of nano-sized (100nm) manganese ceramic material for high voltage pseudo-capacitor]; International Collaborative Energy Technology R&D Program of the Korea Institute of Energy Technology Evaluation and Planning (KETEP) from Ministry of Trade, Industry & Energy of Korea [20138520030800]. Also, SMM acknowledges The Royal Society for financial support.

Figure captions

Figure 1. Illustration of the nanostructures and crystal growth mechanisms of (a) HAR-, (b) MAR- and (c) LAR-NiMoO₄ 1-D nanostructures with different aspect ratios. 1-D nanostructures are systematically controlled by using different supersaturation states during the growth phase. (d-f) SEM images of the HAR-, MAR- and LAR-NiMoO₄ 1-D nanostructures. Inset images show the corresponding TEM images of the three different 1-D nanostructures.

Figure 2. (a) XRD patterns of the as-prepared NiMoO₄ nanostructures. Asterisks show XRD patterns of the nickel foam. (b) Calculated BET specific surface areas of the as-prepared NiMoO₄ nanostructures. (c) Ni 2p and (d) Mo 3d XPS spectra of the as-prepared NiMoO₄ nanostructures. Inset: images show that Ni cations in the octahedral site and Mo cations in the tetrahedral site contribute to the electrochemical reaction and stability, respectively.

Figure 3. (a) CV curves for HAR-, MAR-, and LAR-NiMoO₄ electrodes at a scan rate of 5 mV s⁻¹ in 1.0 M KOH. The inset shows the redox potential gap (ΔE_p) for the different NiMoO₄ samples. (b) Cathodic peak current density as a function of the square root of the scan rate for the three different samples. (c) Comparison of the capacitance retention and (d) Bode phase plots for the HAR-, MAR-, and LAR-NiMoO₄ samples. (e) Illustration of the relationship between the tailored NiMoO₄ nanostructures and the pseudo-capacitive behavior including electrolyte ion diffusion and electron transfer dynamics.

Figure 4. (a) Comparative CV curves of the HAR-NiMoO₄ and AC electrodes at 5 mV s⁻¹ in a three electrode system. (b) CV curves and (c) Cycling stability of the AC//HAR-NiMoO₄ ASC. The inset image shows galvanostatic charge-discharge curves of the ASC. (d) Ragone plot of the AC//HAR-NiMoO₄ ASC in comparison with other reported ASCs.

References

- 1 Wang, G.; Zhang, L.; Zhang, J. A Review of Electrode Materials for Electrochemical Supercapacitors. *Chem. Soc. Rev.* **2011**, *41*, 797–828.
- 2 Yan, J.; Wang, Q.; Wei, T.; Fan, Z. Recent Advances in Design and Fabrication of Electrochemical Supercapacitors with High Energy Densities. *Adv. Energy Mater.* **2014**, *4*, 1300816.
- 3 Simon, P.; Gogotsi, Y. Materials for Electrochemical Capacitors. *Nature Mater.* **2008**, *7*, 845–854.
- 4 Augustyn, V.; Simon, P.; Dunn, B. Pseudocapacitive Oxide Materials for High-Rate Electrochemical Energy Storage. *Energy Environ. Sci.* **2014**, *7*, 1597–1614.
- 5 Fisher, R.; Watt, M.; Ready, W. Functionalized Carbon Nanotube Supercapacitor Electrodes: A Review on Pseudocapacitive Materials. *ECS J. Solid State Sci. Technol.* **2013**, *2*, M3170–M3177.
- 6 Chou, J.-C.; Chen, Y.-L.; Yang, M.-H.; Chen, Y.-Z.; Lai, C.-C.; Chiu, H.-T.; Lee, C.-Y.; Chueh, Y.-L.; Gan, J.-Y. RuO₂/MnO₂ Core-shell Nanorods for Supercapacitors. *J. Mater. Chem. A* **2013**, *1*, 8753–8758.
- 7 Zhu, Y.; Cao, C.; Tao, S.; Chu, W.; Wu, Z.; Li, Y. Ultrathin Nickel Hydroxide and Oxide Nanosheets: Synthesis, Characterizations and Excellent Supercapacitor Performances. *Sci. Rep.* **2014**, *4*, 5787.
- 8 Liu, W.; Li, X.; Zhu, M.; He, X. High-Performance All-Solid State Asymmetric Supercapacitor Based on Co₃O₄ Nanowires and Carbon Aerogel. *J. Power Sources* **2015**, *282*, 179–186.
- 9 Ma, X.; Kolla, P.; Zhao, Y.; Smirnova, A.; Fong, H. Electrospun Lignin-Derived Carbon Nanofiber Mats Surface-Decorated with MnO₂ Nanowhiskers as Binder-Free Supercapacitor Electrodes with High Performance. *J. Power Sources* **2016**, *325*, 541–

548.

- 10 Wu, Z.; Zhu, Y.; Ji, X. NiCo₂O₄-Based Materials for Electrochemical Supercapacitors. *J. Mater. Chem. A* **2014**, *2*, 14759–14772.
- 11 Li, L.; Peng, S.; Cheah, Y.; Teh, P.; Wang, J.; Wee, G.; Ko, Y.; Wong, C.; Srinivasan, M. Electrospun Porous NiCo₂O₄ Nanotubes as Advanced Electrodes for Electrochemical Capacitors. *Chem. - A Euro. J.* **2013**, *19*, 5892–5898.
- 12 Hu, J.; Li, M.; Lv, F.; Yang, M.; Tao, P.; Tang, Y.; Liu, H.; Lu, Z. Heterogeneous NiCo₂O₄@polypyrrole Core/sheath Nanowire Arrays on Ni Foam for High Performance Supercapacitors. *J. Power Sources* **2015**, *294*, 120–127.
- 13 Pendashteh, A.; Rahmanifar, M.; Kaner, R.; Mousavi, M. Facile Synthesis of Nanostructured CuCo₂O₄ as a Novel Electrode Material for High-Rate Supercapacitors. *Chem. Comm.* **2013**, *50*, 1972–1975.
- 14 Peng, S.; Li, L.; Hu, Y.; Srinivasan, M.; Cheng, F.; Chen, J.; Ramakrishna, S. Fabrication of Spinel One-Dimensional Architectures by Single-Spinneret Electrospinning for Energy Storage Applications. *ACS Nano* **2015**, *9*, 1945–1954.
- 15 Li, L.; Peng, S.; Wu, H.; Yu, L.; Madhavi, S.; Lou, X. A Flexible Quasi-Solid-State Asymmetric Electrochemical Capacitor Based on Hierarchical Porous V₂O₅ Nanosheets on Carbon Nanofibers. *Adv. Energy Mater.* **2015**, *5*, 1500753.
- 16 Xia, X.; Lei, W.; Hao, Q.; Wang, W.; Wang, X. One-Step Synthesis of CoMoO₄/graphene Composites with Enhanced Electrochemical Properties for Supercapacitors. *Electrochim. Acta* **2013**, *99*, 253–261.
- 17 Xiao, K.; Xia, L.; Liu, G.; Wang, S.; Ding, L.-X.; Wang, H. Honeycomb-like NiMoO₄ Ultrathin Nanosheet Arrays for High-Performance Electrochemical Energy Storage. *J. Mater. Chem. A* **2015**, *3*, 6128–6135.
- 18 Wang, S.; Sun, S.; Li, S.; Gong, F.; Li, Y.; Wu, Q.; Song, P.; Fang, S.; Wang, P. Time

- and Temperature Dependent Multiple Hierarchical NiCo₂O₄ for High-Performance Supercapacitors. *Dalton Tran.* **2016**, 45, 7469–7475.
- 19 Zhang, G.; Lou, X. Controlled Growth of NiCo₂O₄ Nanorods and Ultrathin Nanosheets on Carbon Nanofibers for High-Performance Supercapacitors. *Sci Rep.* **2013**, 3, 1470.
- 20 Xiang, N.; Ni, Y.; Ma, X. Shape-Controlled Synthesis of NiCo₂O₄ Microstructures and Their Application in Supercapacitors. *Chem. Asian J.* **2015**, 10, 1972–1978.
- 21 Zhu, T.; Koo, E.; Ho, G. Shaped-Controlled Synthesis of Porous NiCo₂O₄ with 1-3 Dimensional Hierarchical Nanostructures for High-Performance Supercapacitors. *RSC Adv.* **2014**, 5, 1697–1704.
- 22 Chithambararaj; Yogamalar, R.; Bose, C. Hydrothermally Synthesized H-MoO₃ and A-MoO₃ Nanocrystals: New Findings on Crystal-Structure-Dependent Charge Transport. *Cryst. Growth. Des.* **2016**, 16, 1984–1995.
- 23 Huang, Z.; Zhang, Z.; Qi, X.; Ren, X.; Xu, G.; Wan, P.; Sun, X.; Zhang, H. Wall-like Hierarchical Metal Oxide Nanosheet Arrays Grown on Carbon Cloth for Excellent Supercapacitor Electrodes. *Nanoscale* **2016**, 8, 13273–13279.
- 24 Yan, J.; Fan, Z.; Sun, W.; Ning, G.; Wei, T.; Zhang, Q.; Zhang, R.; Zhi, L.; Wei, F. Advanced Asymmetric Supercapacitors Based on Ni(OH)₂/Graphene and Porous Graphene Electrodes with High Energy Density. *Adv. Funct. Mater.* **2012**, 22, 2632–2641.
- 25 Ghosh, D.; Giri, S.; Das, C. Synthesis, Characterization and Electrochemical Performance of Graphene Decorated with 1D NiMoO₄·nH₂O Nanorods. *Nanoscale* **2013**, 5, 10428–10437.
- 26 Pang, H.; Wei, C.; Li, X.; Li, G.; Ma, Y.; Li, S.; Chen, J.; Zhang, J. Microwave-Assisted Synthesis of NiS₂ Nanostructures for Supercapacitors and Cocatalytic Enhancing Photocatalytic H₂ Production. *Sci. Rep.* **2014**, 4, 3577.

- 1
2
3
4 27 Senthilkumar, B.; Sankar, K.; Selvan, R.; Danielle, M.; Manickam, M. Nano A-NiMoO₄
5 as a New Electrode for Electrochemical Supercapacitors. *RSC Adv.* **2012**, *3*, 352–357.
6
7
8 28 Mai, L.; Li, H.; Zhao, Y.; Xu, L.; Xu, X.; Luo, Y.; Zhang, Z.; Ke, W.; Niu, C.; Zhang, Q.
9
10 Fast Ionic Diffusion-Enabled Nanoflake Electrode by Spontaneous Electrochemical
11 Pre-Intercalation for High-Performance Supercapacitor. *Sci. Rep.* **2013**, *3*, 1718.
12
13 29 Xu, P.; Liu, J.; Yan, P.; Miao, C.; Ye, K.; Cheng, K.; Yin, J.; Cao, D.; Li, K.; Wang, G.
14 Preparation of Porous Cadmium Sulphide on Nickel Foam: A Novel Electrode Material
15
16 with Excellent Supercapacitor Performance. *J. Mater. Chem. A* **2016**, *4*, 4920–4928.
17
18
19 30 Liu, S.; Hui; Hui Flower-like Copper Cobaltite Nanosheets on Graphite Paper as High-
20 Performance Supercapacitor Electrodes and Enzymeless Glucose Sensors. *ACS Appl.*
21
22 *Mater. Interfaces* **2016**, *8*, 3258–3267.
23
24
25 31 Pendashteh, A.; Moosavifard, S.; Rahmanifar, M.; Wang, Y.; El-Kady, M.; Kaner, R.;
26 Mousavi, M. Highly Ordered Mesoporous CuCo₂O₄ Nanowires, a Promising Solution
27 for High-Performance Supercapacitors. *Chem. Mater.* **2015**, *27*, 3919–3926.
28
29
30 32 Pan, X.; Ren, G.; Hoque, M. N. F.; Bayne S.; Zhu, K.; Fan, Z. Fast Supercapacitors
31 Based on Graphene-Bridged V₂O₃/VO_x Core–Shell Nanostructure Electrodes with a
32 Power Density of 1 MW kg^{−1}. *Adv. Mater. Inter.* **2014**, *1*, 1400398.
33
34
35 33 Yuan, L.; Lu, X.-H.; Xiao, X.; Zhai, T.; Dai, J.; Zhang, F.; Hu, B.; Wang, X.; Gong, L.;
36 Chen, J.; Hu, C.; Tong, Y.; Zhou, J.; Wang, Z. L. Flexible Solid-State Supercapacitors
37 Based on Carbon Nanoparticles/MnO₂ Nanorods Hybrid Structure. *ACS Nano* **2012**, *6*,
38 656–661.
39
40
41 34 Ren, X.; Guo, C.; Xu, L.; Li, T.; Hou, L.; Wei, Y. Facile Synthesis of Hierarchical
42 Mesoporous Honeycomb-like NiO for Aqueous Asymmetric Supercapacitors. *ACS*
43 *Appl. Mater. Interfaces* **2015**, *7*, 19930–19940.
44
45
46 35 Li, X.; Jiang, L.; Zhou, C.; Liu, J.; Zeng, H. Integrating Large Specific Surface Area
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- and High Conductivity in Hydrogenated NiCo₂O₄ Double-Shell Hollow Spheres to Improve Supercapacitors. *NPG Asia Mater.* **2015**, 7, e165.
- 36 Cheng, D.; Yang, Y.; Xie, J.; Fang, C.; Zhang, G.; Xiong, J. Hierarchical NiCo₂O₄@NiMoO₄ Core-shell Hybrid Nanowire/nanosheet Arrays for High-Performance Pseudocapacitors. *J. Mater. Chem. A* **2015**, 3, 14348–14357.
- 37 Wang, X.; Liu, W. S.; Lu, X.; Lee, P. S. Dodecyl Sulfate-Induced Fast Faradic Process in Nickel Cobalt Oxide-reduced Graphite Oxide Composite Material and Its Application for Asymmetric Supercapacitor Device. *J. Mater. Chem.* **2012**, 22, 23114–23119.
- 38 Yang, J.; Li, G.; Pan, Z.; Liu, M.; Hou, Y.; Xu, Y.; Deng, H.; Sheng, L.; Zhao, X.; Qiu, Y.; Zhang, Y. All-Solid-State High-Energy Asymmetric Supercapacitors Enabled by Three-Dimensional Mixed-Valent MnO_x Nanospire and Graphene Electrodes. *ACS Appl. Mater. Interfaces* **2015**, 7, 22172–22180.
- 39 Senthilkumar, B.; Meyrick, D.; Lee, Y.-S.; Selvan, R. Synthesis and Improved Electrochemical Performances of Nano β-NiMoO₄-CoMoO₄·xH₂O Composites for Asymmetric Supercapacitors. *RSC Adv.* **2013**, 3, 16542–16548.
- 40 Ma, X.-J.; Kong, L.-B.; Zhang, W.-B.; Liu, M.-C.; Luo, Y.-C.; Kang, L. Design and Synthesis of 3D Co₃O₄@MMoO₄ (M=Ni, Co) Nanocomposites as High-Performance Supercapacitor Electrodes. *Electrochim. Acta* **2014**, 130, 660–669.
- 41 Xiao, K.; Xia, L.; Liu, G.; Wang, S.; Ding, L.-X.; Wang, H. Honeycomb-like NiMoO₄ Ultrathin Nanosheet Arrays for High-Performance Electrochemical Energy Storage. *J. Mater. Chem. A* **2015**, 3, 6128–6135.

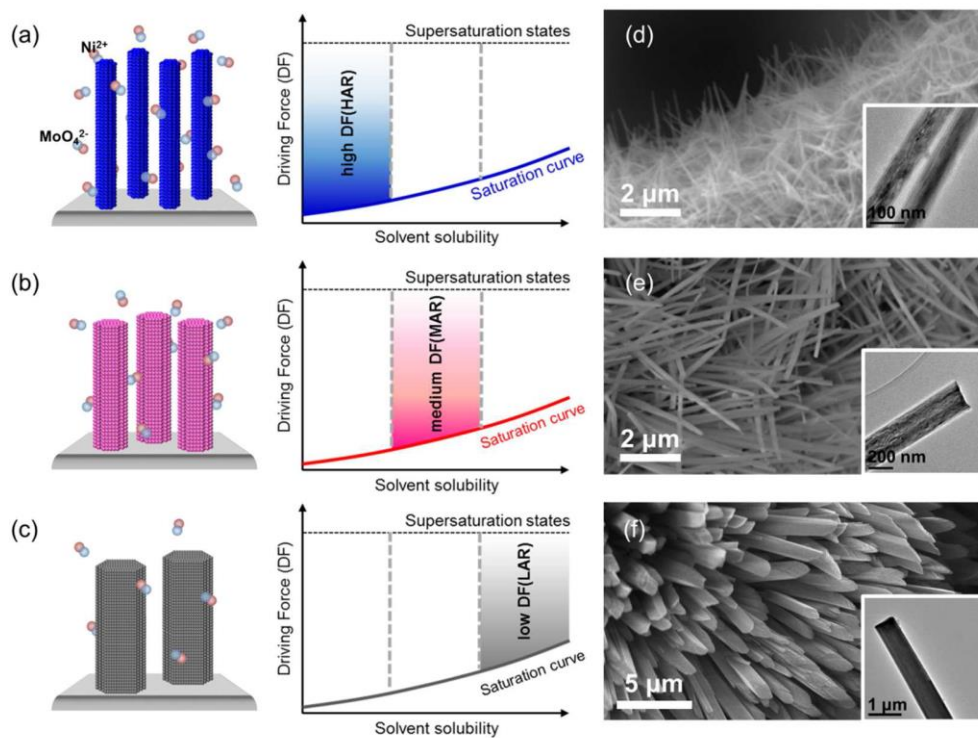


Figure 1. Hong *et. al.*

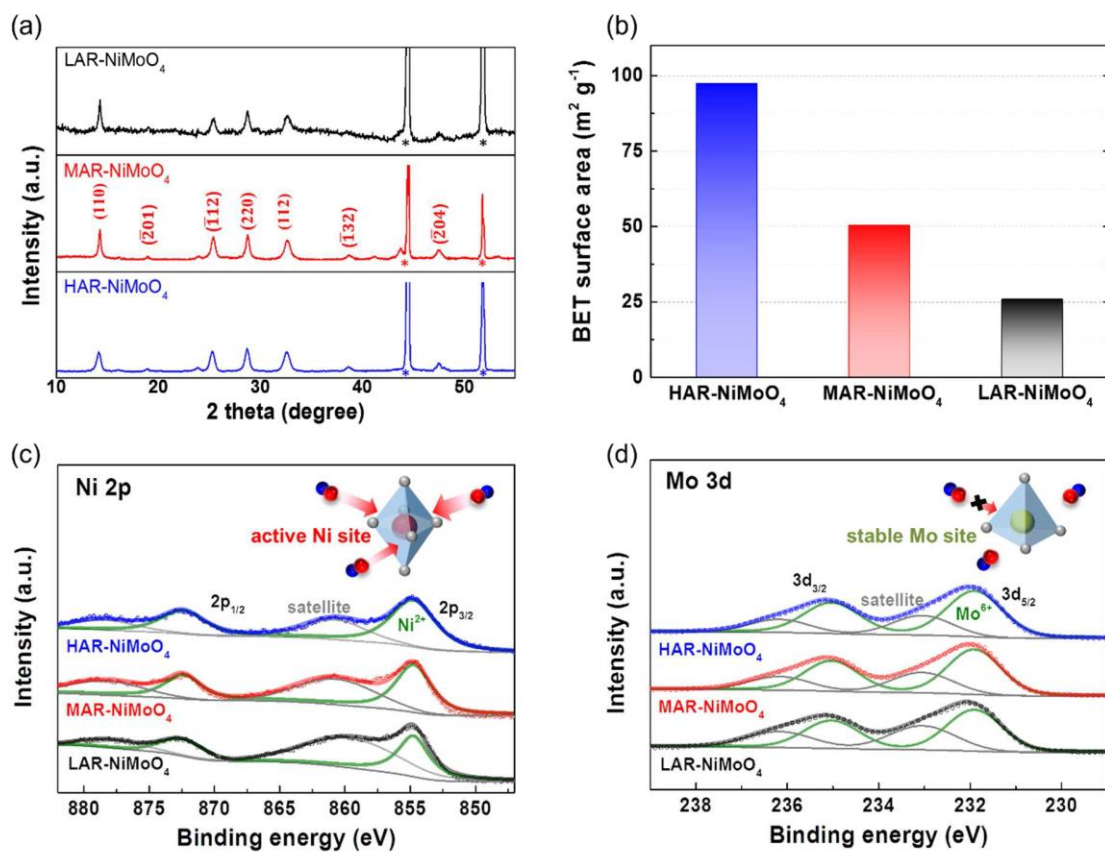


Figure 2. Hong *et. al.*

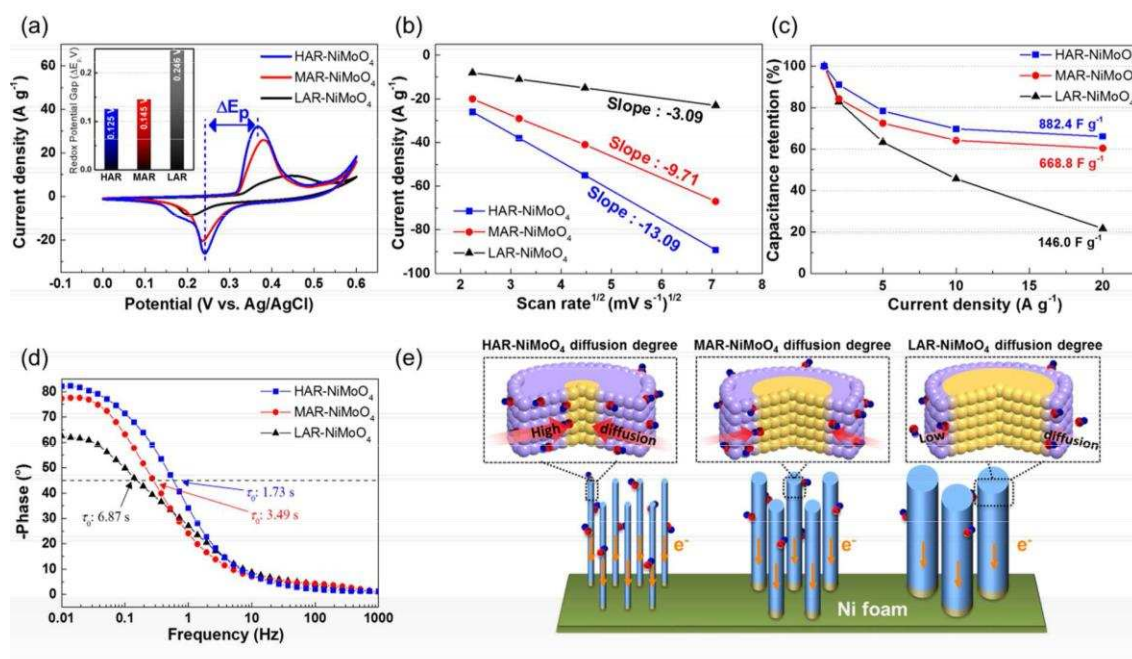


Figure 3. Hong *et. al.*

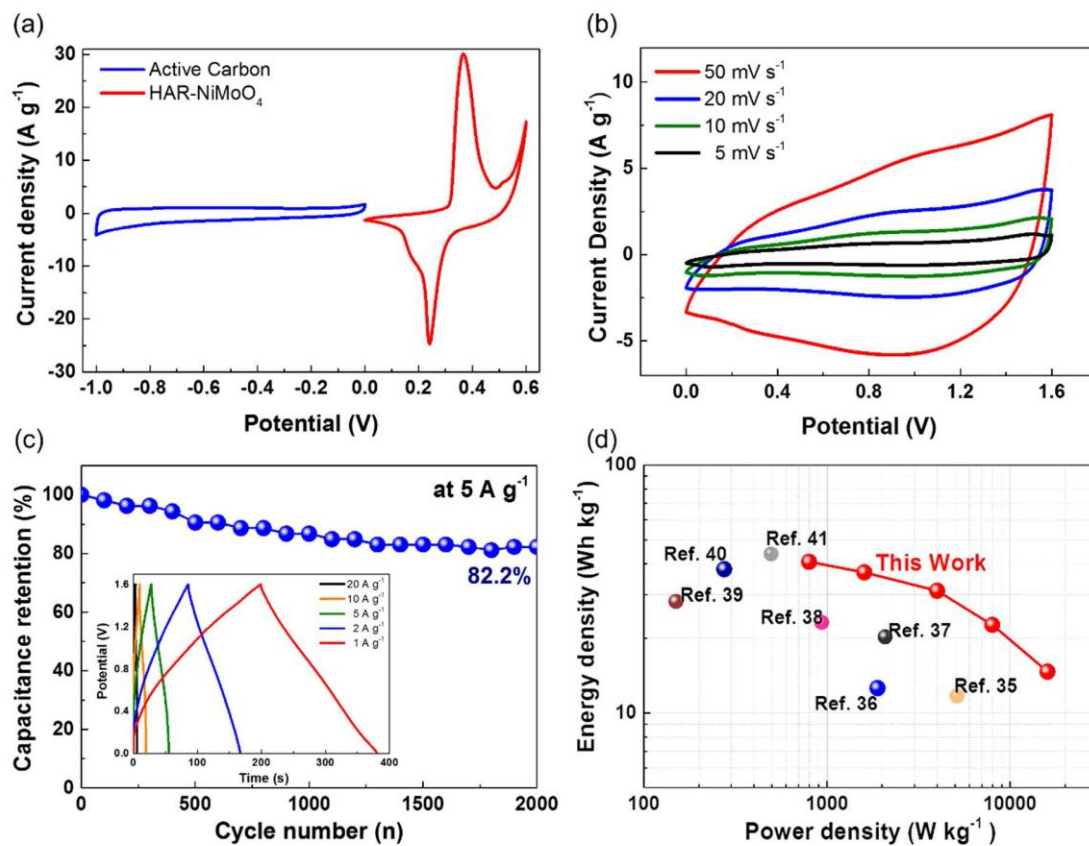


Figure 4. J. Hong *et. al.*

Table of Contents

